

Exponential Temperature Dependence of Penetration Depth in MgB_2

F. Manzano and A. Carrington

H. H. Wills Physics Laboratory, University of Bristol, Bristol, BS8 1TL, England.

(February 1, 2008)

The temperature dependence of the London penetration depth, $\lambda(T)$, was measured in polycrystalline MgB_2 samples by a high-resolution, radio frequency technique. A clear exponential temperature dependence of $\lambda(T)$ was observed at low temperature, indicating *s*-wave pairing. A fit to the data gives an effective energy gap Δ of 2.8 ± 0.4 meV ($2\Delta/k_B T_c = 1.7 \pm 0.2$), which is significantly smaller than the standard BCS weak coupling value of 3.5. This may be explained either by an anisotropic gap or the influence of low frequency phonon modes.

PACS numbers: 74.25.Nf

The recent discovery [1] of superconductivity at 39 K in the binary compound MgB_2 has sparked a large number of investigations into its physical properties. A crucial question is whether its high T_c can be explained by a phonon mediated pairing interaction within the usual BCS-Eliashberg framework. A first step in answering this question is to determine the symmetry of the superconducting order parameter and the nature of the low energy excitations.

Several experiments so far, have given strong indications that the superconductivity is of the *s*-wave BCS type. An important experiment has been the observation of a large boron isotope effect [2]. In conventional superconductors, tunneling measurements played a key role in verifying the BCS theory, however, in the cuprate superconductors this probe has not proved quite as useful because the short coherence length ξ makes junction fabrication difficult. The majority of tunneling measurements on MgB_2 so far show a *s*-wave like gap but the values of the deduced gap vary widely between 2 and 7 meV [3–6]. The magnetic penetration depth λ has proven to be a powerful probe of the gap symmetry in *both* classical and high T_c superconductors and gives unambiguous information about the nature of the low energy excitations in superconductors. As the length scale probed is of order λ rather than ξ , for high κ materials, penetration depth measurements are much less sensitive to surface quality than tunneling, and hence we expect the results to be more representative of the bulk.

There have been several recent reports of measurements of $\lambda(T)$ for MgB_2 by ac-susceptibility [7,8], muon spin rotation [7] and optical conductivity [9] techniques. These authors conclude that at high temperature $\lambda(T)$ follows a power law dependence [$\lambda(T) \sim T^2$ (Refs. [7,9]) and $\lambda(T) \sim T^{2.7}$ (Ref. [8])], which seems to be at odds with tunneling and other measurements which indicate that there is a sizeable *s*-wave gap. In this paper we present high resolution measurements of the temperature dependence of the penetration depth in polycrystalline samples of MgB_2 . We find strong evidence for a predominately exponential temperature dependence of λ at low temperature consistent with *s*-wave BCS behavior. The

gap deduced from fits to the data however, is significantly smaller than the BCS weak coupling value. This may be explained by either a strong anisotropy of the gap or the presence of low energy phonon modes.

Three different types of polycrystalline MgB_2 samples were studied. Samples A and C, were produced from commercially available (Alfa Aesar) powder. Sample A was produced by casting the powder directly in epoxy resin (weight ratio MgB_2 :Epoxy $\sim 1:6.5$). The commercial powder has a relatively wide range of grain sizes which complicates quantitative analysis of the data. For the analysis to give a reliable estimate of the absolute values of $\lambda(T)$ grain sizes $\lesssim 5\lambda$ are required [10]. To obtain such a distribution the commercial powder was ground in an agate mortar and then sedimented in acetone for 1 hour [11]. The resulting powder was then cast in epoxy ($\sim 6\%$ by volume) to produce sample C. The grain size distribution was measured from scanning electron microscope images. The diameter of 96% of the grains was less than $1\mu\text{m}$, and the mean diameter was $0.56\mu\text{m}$. Sample B was fabricated by reacting boron powder and Mg flakes in an Argon atmosphere at high temperature. This procedure produced a dense polycrystalline pellet. X-ray diffraction and scanning electron microscopy showed that as grown samples of type B contained some residual flakes of unreacted Mg. Initial measurements found that this changed the low temperature behavior of $\lambda(T)$ markedly [12]. To remove this contamination we immersed these samples in a dilute solution ($\sim 0.5\%$) of HCL and ethanol. T_c was unaffected by this. Previous studies have shown that the commercial MgB_2 powder is 98% phase pure, the remaining 2% being mostly composed of iron, carbon and oxygen [13]. The susceptibility of these impurities is too weak to effect the results presented here [13,14].

Measurements of penetration depth were performed in a tunnel diode oscillator operating at 11.9 MHz [15], with frequency stability of a few parts in $10^{10} \text{ Hz}^{-\frac{1}{2}}$. For the powder samples in the present work this translates to a resolution in λ of 10^{-12}m . A particular feature of our apparatus is the very low value of the ac-probe field which we estimate to be $\sim 1\mu\text{T}$. Ambient dc fields are shielded

to a similar level with a mu-metal can. Changes in the oscillator frequency are directly proportional to the inductance of the probe coil and hence to the susceptibility of the sample. For single crystal samples, this frequency shift may be directly related to changes in the penetration depth using the known sample dimensions [16]. In general for polycrystalline samples the relation between the measured susceptibility (per unit volume of superconductor) χ and λ is more complicated and depends on the size distribution of the grains. For well separated grains

$$\chi = \frac{-\frac{3}{2} \sum_i \left(1 - \frac{3\lambda}{r_i} \coth\left(\frac{r_i}{\lambda}\right) + \frac{3\lambda^2}{r_i^2}\right) r_i^3 N_i}{\sum_i r_i^3 N_i} \quad (1)$$

where N_i is the measured number of grains of radius r_i [10]. For sample C, $\lambda(T)$ was determined from the measured $\chi(T)$ and grain size distribution by solving Eq. (1) at each point. For samples A and B the wide distribution of grain sizes and (for sample B) the possibility of interconnection between the grains makes a quantitative determination of $\lambda(T)$ impossible. We note however, that if $\lambda(T)$ becomes temperature independent, then so will $\chi(T)$, irrespective of the detailed dependence of $\chi(T)$ on λ and r_i .

In Fig. 1 we show the temperature dependence of χ for the three different samples. For samples A and B, χ was normalized to -1 at low temperature, whereas for sample C, χ was calculated from the measured volume of superconductor and is thus in absolute units. $\Delta\chi(T)$ denotes the change in χ relative to its value at our base temperature ($T=1.4$ K). It is apparent that in all three samples $\Delta\chi(T)$ becomes essentially temperature independent below around 5 K. This is the main result of this paper and is a clear indication of a finite energy gap in all directions in k -space. A large distribution of grain sizes or anisotropy of λ will effect the detailed T dependence of χ (especially at higher temperature) but cannot cause such an abrupt flattening off of $\Delta\chi(T)$.

The material parameters of MgB₂ deduced from other measurements put it firmly in the clean, local limit ($\lambda(0) \sim 0.2\mu\text{m}$, $\xi(0) \sim 50$ Å and mean free path $\ell \sim 600$ Å [17,18]), so $\Delta\chi(T)$ is directly proportional to changes in the London penetration depth (λ_L). For a s -wave superconductor, at sufficiently low temperature, irrespective of the coupling strength, $\lambda_L(T)$ should follow the BCS behavior

$$\Delta\lambda(T) \simeq \lambda_0^e \sqrt{\frac{\pi\Delta_0}{2k_B T}} \exp\left(\frac{-\Delta_0}{k_B T}\right) \quad (2)$$

where Δ_0 is the value of the energy gap at zero temperature and $\lambda_0^e = \lambda(0)$ in the weak coupling case. In Fig. 1 we show a fit of Eq. (2) to the data for the three samples. The fits give consistent values for Δ_0 which average 33 ± 4 K (the uncertainty reflects the different values of

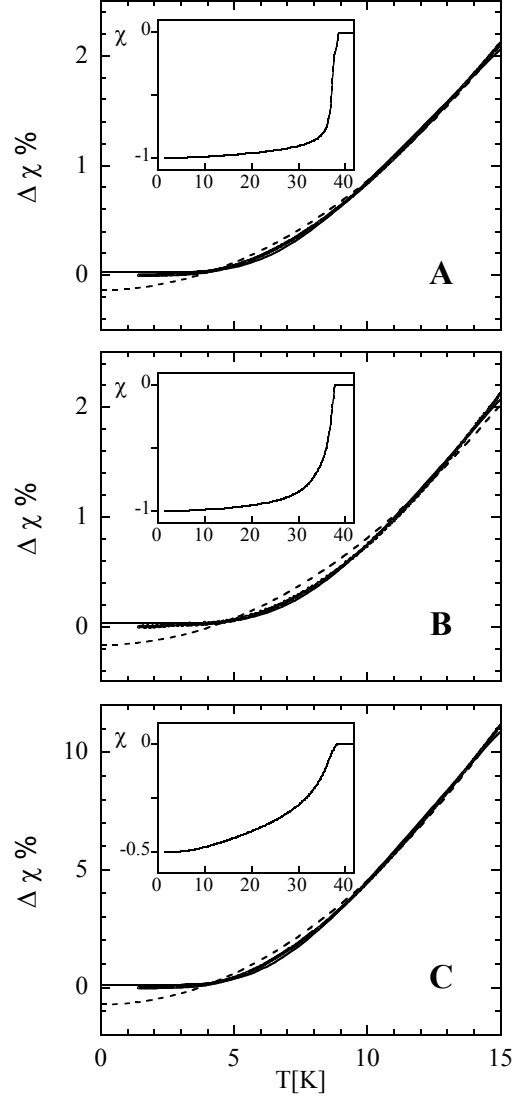


FIG. 1. Temperature dependence of the susceptibility (χ) of samples A, B and C. At low temperature (main panels) $\Delta\chi$ is directly proportional to the temperature dependent penetration depth $\Delta\lambda(T)$. The solid line is a fit to the s -wave BCS form [Eq. (2)], and the dashed line to a T^2 behavior. The insets show $\chi(T)$ over the full temperature range.

Δ_0 between the three samples and as the upper limit of the fit ($T_{\text{max}}^{\text{fit}}$) was varied from 15 K to 20 K). It should be noted that Eq. (2) is not a perfect fit to the data and particularly at very low temperature where the measured $\Delta\lambda(T)$ has a larger temperature dependence that would be indicated by Eq. (2). If taken literally this may indicate the presence of a small amount of excitations with energies significantly below our deduced Δ_0 . However, until high quality single crystals become available it is impossible to rule out extrinsic origins of this term (for instance from weak links at the surface of the grains). The fit improves if two gaps are used (for instance with $\Delta_1 \sim 2\Delta_2$ and the lower gap having a weight of 5% of

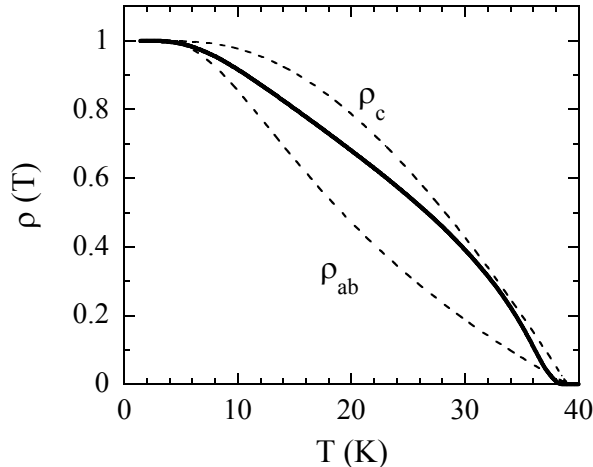


FIG. 2. Temperature dependence of the superfluid density $\rho(T) = \lambda(0)^2/\lambda(T)^2$ for sample C (solid line). The dashed lines are the predictions of the anisotropic gap model (see text)

the larger gap), but this leaves the value of the larger gap unchanged (within the error) from our original estimate.

As mentioned above, several other authors [8,7,9] have claimed that $\lambda(T)$ in MgB_2 does not follow a simple exponential T dependence but rather a power law dependence with an exponent close to 2. In Fig. 1 we show a T^2 fit to data. Clearly, this fit is much worse than the BCS dependence [Eq. (2)]. We have also tried to fit other forms such as $AT + BT^2$ or $AT^2/(T + T^*)$ but both fit the data much worse than Eq. (2) (the latter of these two equations is the form followed by a dirty d -wave superconductor [19]). The key differences between our data and previous studies is our very high resolution, low base temperatures and very low excitation fields.

As described above, for sample C we are able to deduce the absolute values of $\lambda(T)$. In Fig. 2 we show the temperature dependence of the calculated superfluid density $[\rho = \lambda(0)/\lambda(T)]^2$. Our data give a value of $\lambda(0) = 160 \pm 20 \text{ nm}$ which is in good agreement with other estimates [17,8] although is somewhat longer than that deduced from μSR data [7]. The uncertainty in $\lambda(0)$ does not make any significant difference to the temperature dependence of $\rho(T)$. The fit to the low temperature behavior of $\rho(T)$ (Fig. 3) gives values of Δ_0 in the range 28 K to 33 K as $T_{\text{max}}^{\text{fit}}$ was varied from 10 K to 15 K, in good agreement with those extracted from the fits to $\Delta\chi(T)$ in Fig. 1. From this data we are also able to calculate the constant λ_0^e in Eq. (2). We find that, unlike Δ_0 , λ_0^e depends quite strongly on the fitting range - increasing from 57 nm to 90 nm as $T_{\text{max}}^{\text{fit}}$ varies from 10 K to 15 K. This is however, significantly below the BCS value of $\lambda(0) = 160 \text{ nm}$.

MgB_2 has a anisotropic structure, with Mg atoms sandwiched between planar, hexagonal boron rings. It is therefore expected that there will be some anisotropy

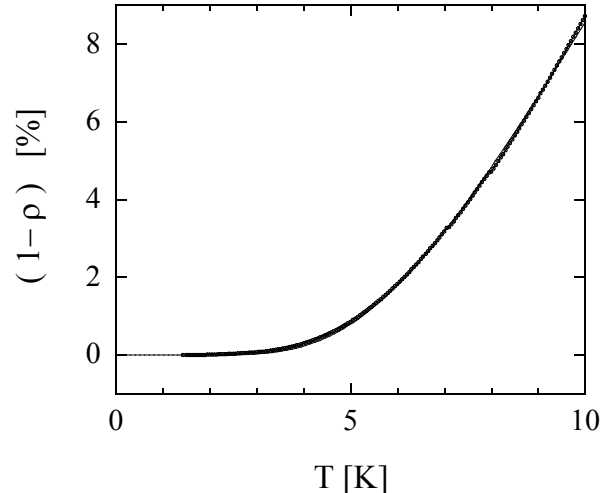


FIG. 3. Low temperature behavior of $\rho(T)$ for sample C along with a BCS fit (Eq. (2)).

between the ab -plane and the c -axis responses. As our measurements have been performed on unaligned polycrystalline samples our measurements of $\lambda(T)$ will be a mixture of the ab -plane and c -axis penetration depths (λ_c and λ_{ab}). Recent results on aligned crystallites and single crystals have shown a significant anisotropy in H_{c2} which implies an anisotropy in the coherence lengths, $\gamma = \xi_{ab}/\xi_c$. In an anisotropic Ginzburg-Landau theory this implies a similar anisotropy in λ , $\gamma = \lambda_c/\lambda_{ab}$. There is some disagreement about the magnitude of this anisotropy, Refs. [20,21] give $\gamma = 1.7 \pm 0.1$ and Refs. [22,23] give $\gamma = 2.6 \pm 0.1$. As far as we know there is no general solution for the moment of a sphere when λ is anisotropic, however solutions do exist in the limits $\lambda \gg r$ [24] and $\lambda \ll r$ [25]. Fortunately, these two limits give similar results for $\gamma \lesssim 3$. To within $\pm 10\%$ the effective $\lambda(0)$ equals $1.2 \lambda_{ab}$ or $1.5 \lambda_{ab}$ for $\gamma = 1.6$ and 2.6 respectively. Our value of $\lambda(0)$ then implies that $\lambda_{ab} = 130 \text{ nm}$ and $\lambda_c = 210 \text{ nm}$ or $\lambda_{ab} \simeq 110 \text{ nm}$ and $\lambda_c \simeq 280 \text{ nm}$, for the two values of γ respectively.

Although the overall temperature dependence of λ deduced from our measurements is consistent with the s -wave BCS picture, the value of the gap obtained is somewhat smaller than the usual BCS weak coupling value ($\Delta/k_B T_c = 1.76$). As pointed out by Haas and Maki [26] a simple explanation for this may be that the s -wave gap is anisotropic. In most conventional superconductors the anisotropy in the pairing interaction is weak ($\sim 10\%$). However, it has been proposed that the unique structure of MgB_2 may produce a significantly enhanced anisotropy [27].

Following Ref. [26] we model the anisotropy in Δ by $\Delta(z) = \Delta\Gamma(z)$ where $z = \cos\theta$ (θ is the polar angle - with respect to the c direction), $\Gamma(z) = (1 + az^2)/(1 + a)$ and a is the parameter which controls the anisotropy. To determine $\Delta\lambda(T)$ in this model it is necessary to first

calculate $\Delta(T)$ self consistently from the gap equation

$$\frac{1}{N_0 V} \int_0^1 \Gamma(z)^2 dz = \int_0^1 \int_0^{\hbar\omega_c} \Gamma(z)^2 \frac{\tanh\left(\frac{1}{2T} (E^2 + \Delta(z)^2)^{\frac{1}{2}}\right)}{(E^2 + \Delta(z)^2)^{\frac{1}{2}}} dE dz \quad (3)$$

and then $\Delta\lambda_{ab}(T)$ from

$$\frac{\Delta\lambda_{ab}^2(T)}{\lambda^2(0)} = 6 \int_0^1 \int_{\Delta(z)}^\infty \frac{df(E)}{dE} \frac{E}{(E^2 - \Delta(z)^2)^{\frac{1}{2}}} z^2 dz dE \quad (4)$$

and similarly for $\lambda_c(T)$ (f is the fermi function). The temperature dependence of $\Delta\lambda(T)$ measured on unaligned polycrystalline samples can then be calculated by a suitable average of $\Delta\lambda_{ab}$ and $\Delta\lambda_c$. For moderate to high anisotropy the low temperature behavior is dominated by $\Delta\lambda_{ab}$ as in this model the gap is smallest in the plane. The resulting T dependence of λ may then be fitted by Eq. (2) with an effective gap which is approximately equal to the minimum gap in the model (the in-plane gap). We find that in order to explain the experimentally determined value of $\Delta/T_c = 0.86 \pm 0.1$ we need $a = 2.2 \pm 0.4$, or a total gap anisotropy $(1+a) = 3.2 \pm 0.4$. Whether or not this very strong anisotropy may be explained by a phonon interaction alone needs to be addressed by microscopic theories. This anisotropy implies a significant difference in the temperature dependence of both $\lambda(T)$ and $\rho(T)$ between the in-plane and out-of-plane directions. The different T dependencies of $\rho_c(T)$ and $\rho_{ab}(T)$ calculated from this model for $a = 3$ are shown in Fig. 2. It should be noted although the detailed behavior will be different if strong coupling corrections and fermi velocity anisotropy are included, the qualitative difference between $\rho_c(T)$ and $\rho_{ab}(T)$ will remain. As our measurements were made on unaligned polycrystals, our data will be an average of $\rho_c(T)$ and $\rho_{ab}(T)$ (the weights depending on anisotropy in $\lambda(0)$). Only a qualitative comparison is possible, but it can be seen that the measured $\rho(T)$ falls between $\rho_c(T)$ and $\rho_{ab}(T)$.

A different approach has been taken by Manske *et al.* [28], who have calculated the tunneling density of states from first principles within a standard Eliashberg theory. Their calculations suggest that the small value of Δ_{min}/T_c is due to a pronounced low frequency dependence of $\Delta(\omega)$ originating from a low-frequency phonon mode. The size of the minimum gap they calculate is in broad agreement with tunneling and our data.

In conclusion we have presented a study of the penetration depth of polycrystalline MgB₂ samples. In agreement with other direct probes of the symmetry of the order parameter we find that $\lambda(T)$ is well described by the usual s -wave BCS behavior, but with a gap that is significantly below the weak coupling BCS value. If this is to be ascribed to a simple anisotropy of the gap then

we find that a fairly large anisotropy of around 3 is required. Alternatively the recent calculation of Manske *et al.* [28] may also explain our data without the need for significant anisotropy in $\Delta(k)$. Further studies on single crystal samples or aligned polycrystallites will help to clarify this question.

We thank R.W. Giannetta, R. Prozorov, K. Maki, N.E. Hussey, J.F. Annett and J.R. Cooper for useful discussions, and P. Timms for providing the type B MgB₂ samples.

-
- [1] J. Nagamatsu *et al.*, Nature **410**, 63 (2001).
 - [2] S.L. Bud'ko *et al.*, Phys. Rev. Lett. **86**, 1877 (2001).
 - [3] F. Giubileo, D. Roditchev, W. Sacks, R. Lamy and J. Klein, cond-mat/0105146.
 - [4] C.T. Chen *et al.*, cond-mat/0104285.
 - [5] G. Karapetrov, M. Iavarone, W.K. Kwok, G.W. Crabtree, and D.G. Hinks, Phys. Rev. Lett. **86**, 4374 (2001).
 - [6] G. Rubio-Bollinger, H. Suderow, S. Vieira, cond-mat/0102242.
 - [7] C. Panagopoulos *et al.*, cond-mat/0103060.
 - [8] X.H. Chen, Y.Y. Xue, R.L. Meng, and C.W. Chu, cond-mat/0103029.
 - [9] A.V. Pronin, A. Pimenov, A. Loidl, S.I. Krasnovobodtsev, cond-mat/0104291.
 - [10] A. Porch *et al.*, Physica (Amsterdam) **214C**, 350 (1993).
 - [11] N. Athanassopoulou, Ph.D. thesis, University of Cambridge (1994).
 - [12] R. Prozorov *et al.*, unpublished.
 - [13] Y. Wang, T. Plackowski, and A. Junod, cond-mat/0103181.
 - [14] J.R. Cooper Phys. Rev. B **54**, R3753 (1996).
 - [15] A. Carrington, R.W. Giannetta, J.T. Kim, and J. Giapintzakis, Phys. Rev. B **59**, R14173 (1999).
 - [16] R. Prozorov, R. W. Giannetta, A. Carrington, and F.M. Araujo-Moreira, Phys. Rev. B **62**, 115 (2000).
 - [17] D.K. Finnemore *et al.*, Phys. Rev. Lett. **86**, 2420 (2001).
 - [18] P.C. Canfield *et al.*, Phys. Rev. Lett. **86**, 2423 (2001).
 - [19] P.J. Hirschfeld and N. Goldenfeld, Phys. Rev. B **48**, 4219 (1993).
 - [20] O.F. de Lima *et al.*, to appear in Phys. Rev. Lett. ; cond-mat/0105332.
 - [21] C.U. Jung *et al.*, cond-mat/0105330.
 - [22] M. Xu *et al.*, cond-mat/0105271.
 - [23] S. Lee *et al.*, cond-mat/0105545.
 - [24] V.G. Kogan, J.R. Clem, Jap. J. Appl. Phys. **26**, 1159 (1987) suppl 26-3; A.M. Neminsky and P.N. Nikolaev, Physica C **212**, 389 (1993).
 - [25] Y.A. Kufarev and E.B. Sonin, Physica C **235**, 1813 (1994).
 - [26] S. Haas and K. Maki, cond-mat/0104207.
 - [27] K. Voelker, V.I. Anisimov, and T.M. Rice, cond-mat/0163082.
 - [28] D. Manske, C. Joas, I. Eremin, and K.H. Bennemann, cond-mat/0105507.